

Gold enrichment in Staffordshire Hoard K370: results of SEM-EDX analysis


Object Type Hilt Collar
 Date 620-650
 Decoration Filigree Glass
 Garnet Other



SEM-EDX analysis was undertaken on the gold sheet at the base of the hilt collar which is part of a set of fittings from a seax handle.

Area analysed	No of analyses		Wt% Au	Wt% Ag	Wt% Cu
Surface	10	Average	84.5	14.0	1.5
		Standard Deviation	0.67	0.59	0.16
Scratch	6	Average	82.4	16.2	1.4
		Standard Deviation	0.53	0.49	0.07
Sub-surface	12	Average	82.1	15.3	2.6
		Standard Deviation	0.56	0.56	0.16

SEM-EDX surface and sub-surface compositions (the results are normalised). This analysis was carried out as part of the gold enrichment study. For full details of methodology and associated results see report PR07444-10 and PR07444-15

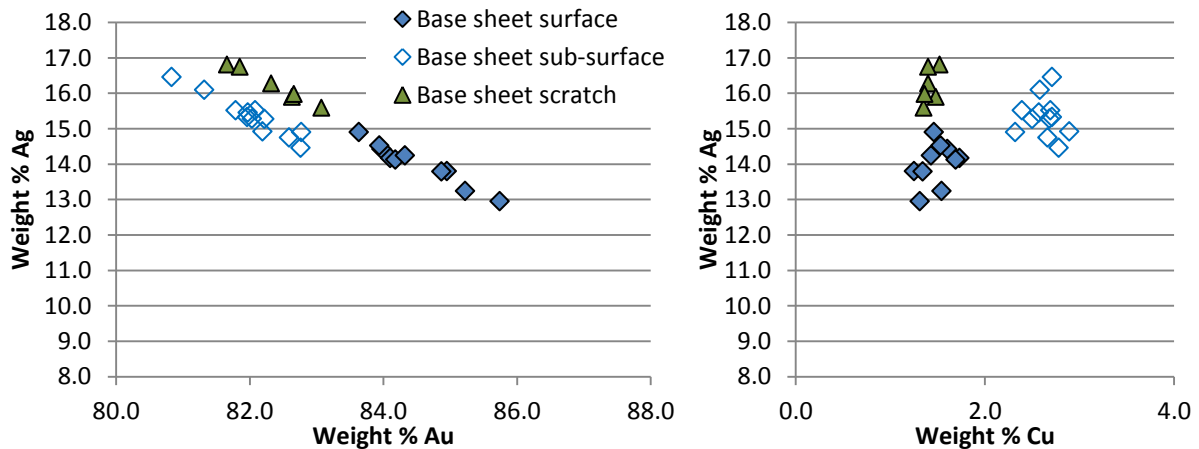

Plots of gold vs silver and copper vs silver contents, based on SEM-EDX analysis, showing the differences between the sub-surface and surface analyses.

SEM-EDX analysis of the sub-surface indicated a composition of approximately 81-83 wt% gold, 14-16 wt% silver, the rest being copper. The analysis revealed a c.1.3 wt% loss of silver from the surface (a difference of c.9% from surface to core), which could be indicative of treatment to deliberately enrich the gold colour of the metal. Only copper and small amounts of silver are normally lost from the surface during burial. The surface of the scratch had a similar composition to the subsurface, but with a similar loss in copper to the other surface analyses, which is likely due to corrosion, confirming that the treatment was carried out prior to burial.

Eleanor Blakelock
 Analysed September 2013

This report contains unpublished research. Its contents should not be published without the permission of the Keeper of the Department of Conservation and Scientific Research.