

E

Cramond [CR 71 CG 66 joining CR 78/V 4② 47, 8K] L-facing. Dr. c25cm

47 is a flange fragment; hard, fine-textured, red-brown fabric; fair quantity of inclusions fairly well-sorted quartz with occasional larger quartz and black fragments (upto 1mm); white streaks and micaceous fragments (do not react with dilute HCl); also ^{tiny} long voids.

Interior grit; quartz, red-brown and blackish fragments (^{2-3mm}) and opaque cream fragments. Thin cream slip. △

Cramond [from Paul Bidwell - Cramond Project v/s Find no.

136] flange fragment. Hard, ^{fairly} fine-textured, orange-brown with lighter brown nr. surface, can be micaceous. It had matt, red-brown slip. PTO (9K)

continued (9K)

Inclusions occasional are thin streaks probably clay; moderate, tiny to small transparent quartz & rare opaque orange-brown & black material with occasional larger grits.

2 fragmentary stamps upside down to each other

Carriden [CE 94-4 From F.14, layer II - small ditch across entrance 1K. Sent by G. Bailey Falkirk Museum] r-facing 2 stamps impressed close together FEE/FEC. Dr. 28 cms. Self-coloured slip. Orange-brown fabric with darker reddish-orange core. Inclusions: large ^{very prominent} sporadic white inclusions which are probably refined pottery (Dr Gaunt no.9) up to .5 cm across. These inclusions appear to contain quartz grains; also quartz, dark red vesicular and perhaps other materials described among the tinteration grit. For tinteration grit see Jeff Gaunt's description.

Cameron [unregistered; NMA; 60K] r. facing; stamped twice together;
red fabric + surface; flaked on part of inside beneath spout; largish
to smallish, white, r/b, black, grey grit.; near 46K NMA but
rounded flange. no rubbing

Newstead [p. 266, fig. 35, no. 8; FRA 1459; 110K NMA] soft, orange fabric
with brownish red surface; abundant grey, black, white grit to just
below b.b.

Newstead [FRA 1459; unpublished; 114K NMA] reddish pink core
changing to cream near surface; similar to 110K but different vessel;
stamp worn.

EM[-.]

9.

Cameron [AOC exc" 2011. Project 21797 vicus (Fresco development)

Glasgow Rd CN 11) Project 21797. Context 1461 Find no. 235.
306 g w/ Diam 320 mmns 19% Very hard, red-brown
fabnd with darker core & cream slip. Moderate to fairly
frequent, mostly tiny quartz inclusions in ^{occasional} (small)
~~medium~~ to ^{large} moderate-sized black, red-brown and quartz
Int grit; includes different types of quartz and sand
stone & some black rock. Attributed to Inveresk.
Right-facing stamps impressed close together.
Well-worn.

JOINS no 32.

Camelon [⑯ CAM 76 DG Site C 17.9k] FF. Stamped twice EEC.
~~pinkish-~~

Pinkish fabric; fired to cream at surface, streaked cream in
 interior; moderate ^{ill-sorted} inclusions quartz + orange-brown fragments.
~~yellow orange-brown~~
 No trituration grit survives; ~~orange-brown~~ slip.

Camelon [⑯ CAM 76 ED Site A 41.10k] FF. ^{L. facing ✓} Pinkish-brown fabric
^{layers from 2.5yr b1.8 to}
^(5yr 7/8), fine textured and micaceous; sparse inclusions
^{ill-sorted} quartz, red-brown and white fragments. No trituration
 grit survives but fragments of quartz and red-brown

^{self colored slip.} on flange. Dr. c. 29 cm. traces of thin pale slips. Could be same
 fabric as above. Can be assigned to the L. facing I think probably r. fac
 JOINS ⑯ + 97 Site A 50 layer 6 77 EO + 76 PX

EMI

Rodding 3 vessels

STAMPS FROM SCOTLAND.

Macdonald p. 456. "EME".

Balmuildy [pl. xl, B. 4 and p. 78; F. 1922.315; D. 3. Hunterian M. 11K] L-facing
cream fabric with pinkish tinge; cream slip mostly gone; soft fabric; medium,
black, grey, + brown grit to c. $\frac{1}{2}$ " b. b. b.; Type 2b, Balmuildy, but groove
under bead a bit big.

Balmuildy [pl. xl, B. 5 + p. 78; F. 1922.322; Hunterian M. 22K] pink
fabric with thin grey core; hard, no slip visible; 1 or 2 black grits; FEC
twice close together

AS

Macdonald p. 456.

Balmuildy [pl. xl, B. 5 + p. 78; F. 1922.323; Hunterian M. 238] L-facing;
fine, pink buff fabric; no slip visible; much white, black, ?brown, ?grey.
Exact type as 22K but much bigger. FEC twice, close together.

S. N. Miller The R. East at Balmuildy 1922 Glasgow

Pl. XL no. 4 120 (EMG at Wilderhope mentioned).

Uncert

Ardoch [FQ .6.4; NMA .25K] stamped twice together faintly; soft, orange

buff fabric; medium + greyish, fair amount on piece, black + grey grits to b.b.

Newstead [p.266, f.35, see no.7; FRA 1458; VII. 15.52; NMA .128K] flange
fragment; hard, red fabric; cream slip. *tra. q.*

Cameron [Folklink Museum.] light red fabric with cream slip; tabbing GW.

Newstead [NMA .xc] accession number (1965. found packed in cellar) *v. no. 7*.

Sketch. Coarse, drab, greyish cream inside; greyish drab outside;
core brownish; surface slips brown; medium, brown, grey, translucent
(? flint) grey grit. ³³⁷ FRA 2369 Pt 91.

FRA 3044

Newstead. [NMA .(x 1965 in cellar)] flaked in parts. Creamy buff fabric with thick pink
core to rear surface. Grit in fabric but still a bit soft; brownish buff slip; flange bead only.

Old Kilpatrick [see pl. xviii. B2 + p. 42; 1928.321; Hunterian Mus. 50K] coarse, red fabric with cream slip; flange + head only; lighter fabric of same type as 49K.

Old Kilpatrick [pl. xviii. B2 + p. 42; F1928.323; Hunterian Mus. 49K] flange fragment; fabric + shape as 44K and could be same vessel.

Bothwellhaugh [F. 1940.65; Hunterian ^{? FN} Mus. 96K] l. facing; stamp worn almost away; outside half orange, inside half grey; soft, fairly compact but with gritty parts in fabric; traces of cream slip; largish to small black, brown, grey grit. △

Castledykes [1953 (12); Hunterian Mus. 97K] flange + tiny bit of head; hard, pink fabric with thickish buff core, + buff surface where not purphish brown.

Castledykes [CAS 1954 (14); Hunterian Mus. 99K] l. facing; orange buff fabric, some, medium + smaller, moderate, white grey grit; buff slip. Specimen

The Roman Fort at Cawthleykes. Anne S. Ross.

~~Oliver~~ Edin & London

1964

fig. 46 no. 2.

no 13 etc

Newstead [p. 266, fig. 35, no. 31; FRA 1483; NMA 116K] slightly sandy, buff fabric with pink-brown core; no grit or fragment; with graffiti.

^{" public. says Pit 46}
Newstead [p. 266, fig. 35, no. 7; FRA 1429; VII. 15. 11; NMA 140K] Pit 45;
1 stamp each side of spout; restored; red-brown fabric with cream slip;
abundant, grey, white + brown grit to near bead; 1 POT

Inveresk [no. no; NMA 164K] red fabric with cream slip, medium, brown +
grey grit. FR 730

^{no 2 3 examples.}

Old Kilpatrick [Pl. XVII B: 2 + p. 42; F. 1928, 320; Hunterian M. 44K] coarse, red fabric,
with cream slip; smallish, brown, black, white grit to bead.

A Roman Frontier Post & its People by J. Curle.
(The Fort at Nentwistle in the Parish of Melrose)

p. 26b Vol. 2

(Glasgow MDCCCCXI = 1911)

Fig 35 m7 M?

no 8) 3-7

) 37

no 31 VIR I AV
ognaffo. ~~FEW~~

EMI

Inveresk/Horseleburgh [M13 PPCH 3 / zone II 4.7K] ✓ (facing)
FEC 4.90g diam. 250 42% well-worn. Doab cream
FEC fabric with ochre overtones in the fabric with
darker cream slip. Fractisions: moderate, ill-sorted,
rounded quartz, red-brown and black material.
Intervatian grit: well-mixed, smaller to medium-sized
rounded quartz, red-brown sandstone, fewer black
& probably other rocks.

EMI

2 fingerprints understamps

Inveresk (Musselburgh) [PPCM M11 3/10-11 46K] l. facing
290g Dr. 260 14% l. facing, but no part of spout surviving.
A borderline product - a second - extra hard, overfired to
brown. Very hard, brown with matt, self-coloured slip.
Inclusions: fairly frequent, vari-sized tiny to small transpired
quantities of black material; Sporadic, small to large white
(non-reactive) which is full of ^{tiny} quartz grains. (Does heating
to high temp. make limestone non-reactive?) Intervations is
well embedded so partially covered. It looks unworn:
~~mostly~~ mostly transparent & white quartz, with some black, probably
more than one sort of red-brown to bone sandstone, rare (S)
purple-red ? haematite - ~~red~~

Inveresk [See Br.H.7. N.H.A. 1967 FR. 785. Pink buff core, yellow


outside; mixed w. worn brown + white grits; orangy slip.

Inveresk $\left[\frac{110}{110}^5 + \frac{(43)}{(43)} + \frac{293}{293}^2 + \frac{290}{290}^4 + \frac{432}{432}^3 \right] 23NK$ r. facing.

Pr. 10.3 cms. A second, overfired & muddy brown, black in bottom, warped but usable, dark red + black core; cream slip, white + transparent quartz temper, fabric very hard with white flecks in it; intercalation white quartz + transparent quartz). Black + red brown.

A


EMI
Inveresk [Final civilian FV67 31K] m.facing. 200g
Diam. 25cm. (15%) Hard, creamy brown fabric with streaks
of white through it and fired to cream at the surface,
with thick matt brown slip. Inclusions: moderate to fairly
frequent, ill.-sorted, include quartz, orange-brown material,
brown, and possibly blackish sandstones with some dense
black material. Intervariant grit includes quartz,
probably red-brown & black sandstones and black,
possibly igneous rock. Stamped twice close
together [M] [EEC]. Two fingerprints under rim & stamp.

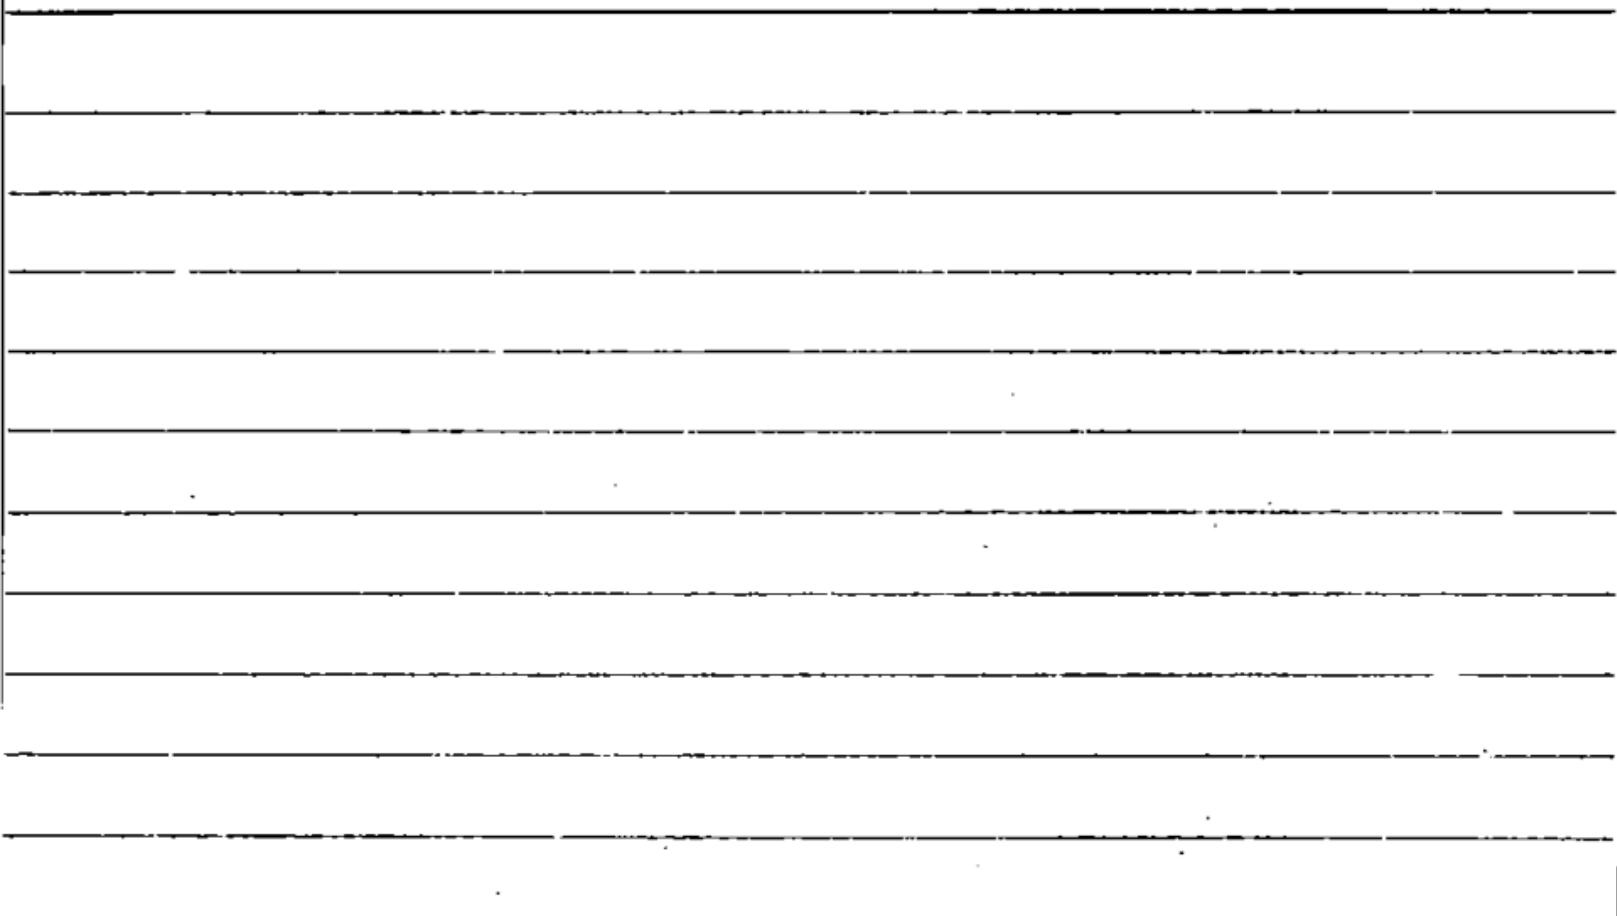

EMI

Invesk [FV 163 J. Done Mike Bishop 4OK] L.-facing.

35g Quite hard, fired to clear near surfaces but pale brown with orange streaks barely showing in it. Self-coloured or self-coloured slip. Inclusions: moderate to fairly frequent, ill-sorted, mixture, some transparent and white quartz, red-brown s.s., few black, very large white possibly clay pellets(?). Interversion grit: few survive, quartz with hackly fracture, red-brown s.s. Few survive.

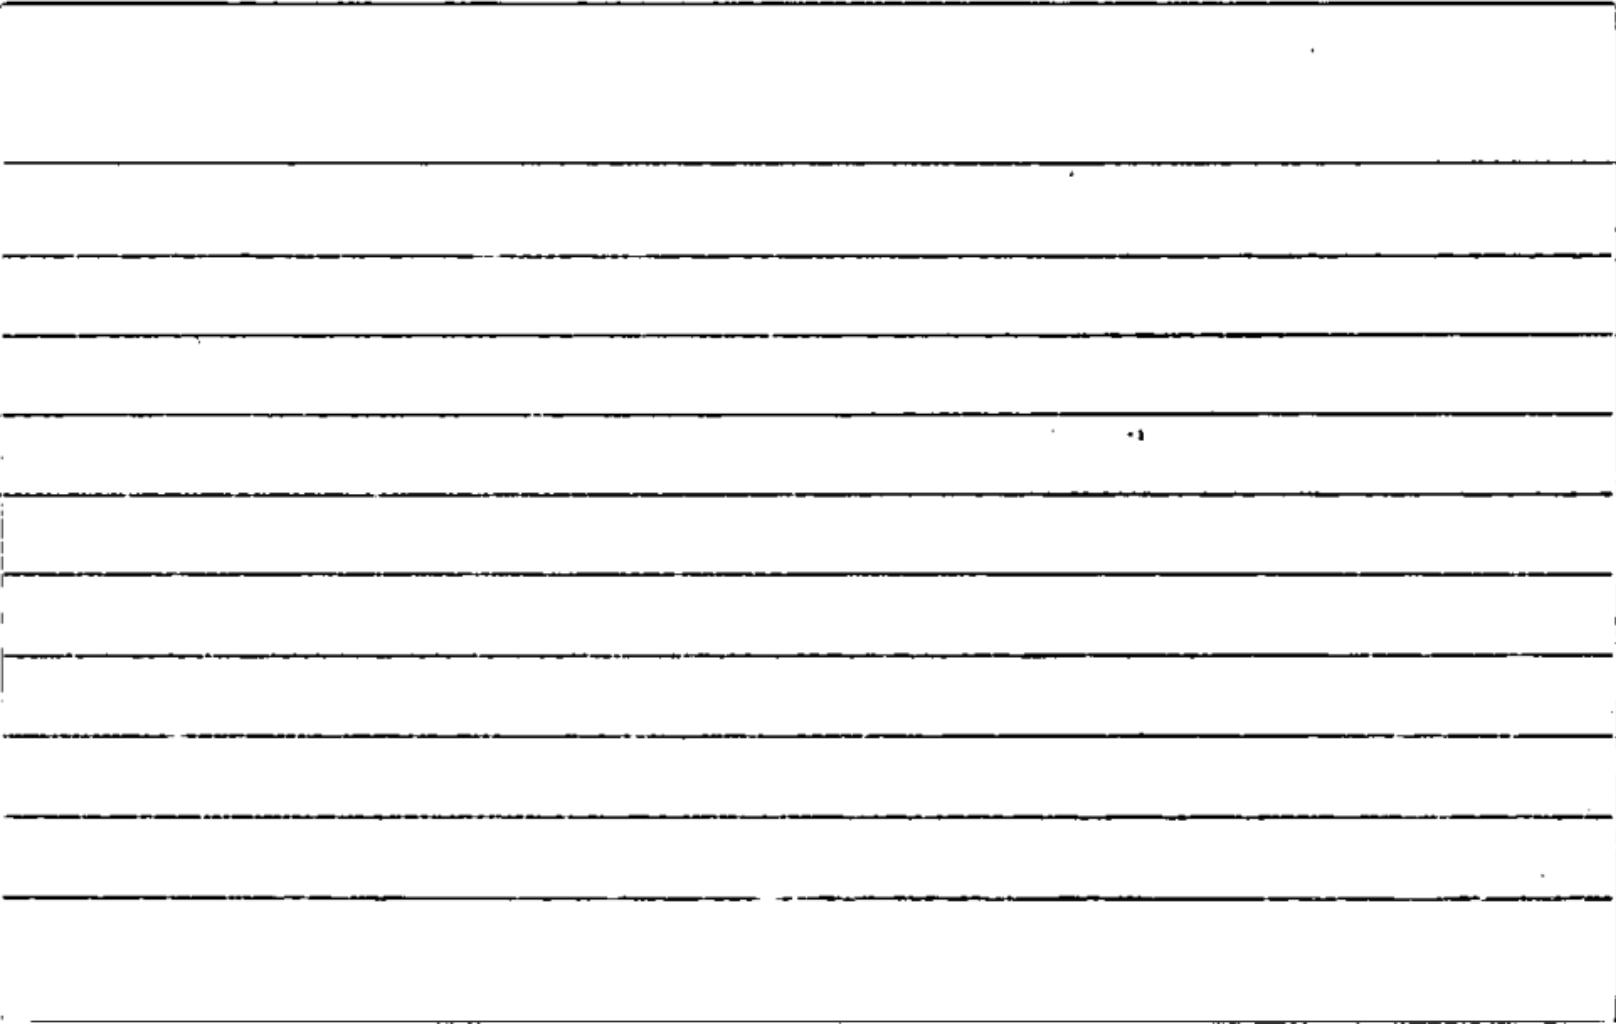

EMI
Inveresk [FV496 First civilian 33K] FF overfired like FV
4.89 and with two namestamps of EMI like FV 489 (32K).
Possibly part of 32K but if so the rim has changed
a lot around the rim.

Inveresk [FV489 Site 1799 Area A F no. 1418. Find no 49]
in Box no 29. 32K] r. Facing. 650g. Diam. c 29cm.
(16%) . Almost complete base and $\frac{1}{2}$ of rim survives in 16 joining
fragments. Heavily overfired, very hard, fine-textured
fabric. The outside skin shows it was intended to be
orange- to red-brown; no indication of slip survives.
Inclusions: moderate, ill-sorted quartz + black material.
Abundant, small to medium - sized tituration grit includes

a lot of quartz but also much of the same material as FV67. Plunge not well formed; overprinting enough to show it's a technical weaker but could have been worn. Well-worn. Fv496 could possibly be from it but rim-profile differs if so.

EMI

Inveresk (Musselburgh) [M4 3-Zone 4 PPCM 45 NK] IRS 50g

Hard, orange-brown fabric with remains of cream slip.

Inclusions: moderate to fairly frequent, ill-sorted, quartz, some red-brown + black. No fnt survives. (S)

Inveresk (Musselburgh) [M8 3-Zone 5 PPCM 45 NK] FF.

35g horizontal streaks in stamp. Black accretion on part (S)
of the end of flange.

Hard, o/b fabric with thin cream slip
Inclusions: moderate to FF, tiny to small, quartz, black

EMI Altib. Scotland
Inveresk [midden between military and 1st. curian FV 1409

34K] FF. Hard, orange-brown fabric, fired to a paler colour at the surface and cream slip. Ill-sorted, moderate to fairly frequent inclusions composed of quartz and opaque, vesicular black material stamped ^{2YR} close together. (Munsell ^{2YR} 6/8 in orange brown core. 'lightened' near surface 7·5 YR 7/6 'reddish-yellow'. 20 grams

Inveresk [Final curian occupation. FV 62 35K] FF_{20g.} with cream slip. Orange-brown (Munsell 2·5 YR 6 7/8) fired to buff near surface (Munsell 7·5 YR 7/6 'reddish-yellow') inclusions: ill-sorted quartz + rare orange-brown + black (vesicular) material. Part of one stamp survives. different pot I think.
PTO

Thought to be EMI - does not exactly

EMI

Inversik/Huselburgh [M19 PPCM 4.9K] v & k facing - 290mm² drain
380gms 32% ^{EMI} _{EMI} // FEC Orange-brown fabric, hard. Clean
slip. Inclusions: moderate, random, ill-sorted, mostly
black, with some red-brown then quartz. Interactions:
mixed, quartz, black rock, quartz sandstone,
probably other rocks. Not worn on piece but broken
high.

Inversik/Huselburgh [M14 PPCM 4.8K] L. facing EMI/FEC Some
~~burning~~ black staining on inside and over onto flange in one part.
Well-worn. Orange-brown fabric, hard, with thin clean slip.
Inclusions in formless streaks of clean clay; few visible grits

red-brown and black. Intercalated; mixed, red-brown sand^{stone},
Transparent and milky quartz, quartz sandstone,
some black. 830g. Diam 280 m. 50%

Graffiti on edge of flange L XI or I XI

These are patches of red-brown slip, certainly around
the spout and elsewhere. ~~It~~ It may have been all
over, it is not possible to say, but it is on top of the cream
slip!

? another (old card)

Ardoch [unregistered; N.M.A. 17K] stamped twice together; hard, orange

fabric with cream buff slip; few, brown + grey grits on flange fragment

Ardoch [unregistered; N.M.A. 20K] hard, orange fabric with red surface;
abundant, medium-sized, white, grey, black grit to 10.0; fairly near 17K

Rough Castle [1920 ^{Macdonald p. 456:4} unregistered; N.M.A. 33K] l. facing; slightly orangy
buff fabric with pink core; flange + spout fragment; surface pink,
end of flange black "FEC".


Cameron [FX. 234 N.M.A. 46K] orangebuff fabric with black core; grey,
+ white grit put in roughly. Worn bbing on the

Cameron [FX 235 N.M.A. 49K] flange fragment; orange fabric with grey
core with buff surface; very like 46K? same pot. Chaffing

EMI

SCOTLAND

Cameron [② CAM 76 ED] Site A [④] joins ⑦ (CAM 76 DX) Site A
and (3 young sherd)^{TIME} and ⑨ (CAM 76 EO) Site A] 10K
n. facing EEC. SEE OLD CARD & REPORT.

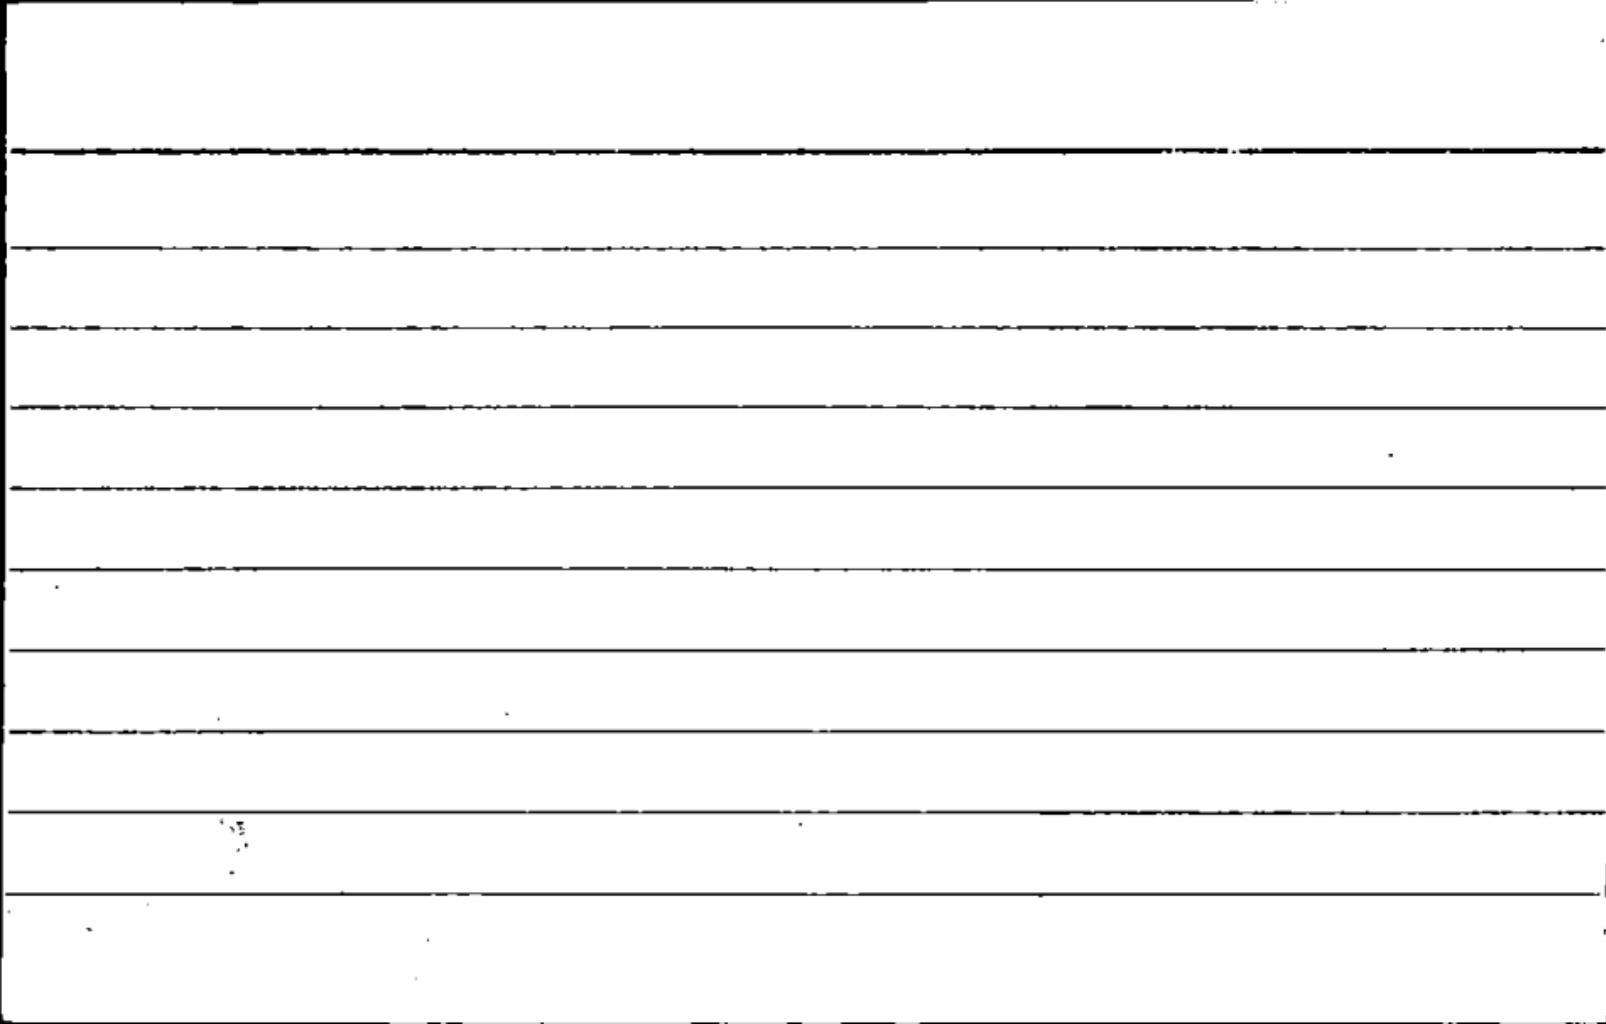

EMI

* = attributed to

Newstead [FRA 302.2 P. 27/28 dms. NMA] Badly cracked worn sport
twisted cracking under flange. Hard, orange-brown fabric with
buff slip; grey, red-brown, probably transparent and opaque
white grit.

* Bothwellhaugh. [1976. 140 & 141] Glas. Arch. J. 8, 1981, 88 fig 27,
no. 56 or p. 90 no 56] Probably the two stamps from 1 vessel; both in
poor condition & incomplete. See other entry

~~Answers~~ Atttributed EMI

Scotland

Bothwellhaugh [1976 140] Bath-house. Hunterian M). Orange-

brown fabric with fine quartz tempering; greatest r/b grit. Green slip B
Fabric probably slightly micaceous. Fabric closely similar to
TM 66 at Bothwell (? border of Antonine) ✓ See after
writing

1976 141 probably other side of pot from 140.

Newstead [1987 R. Jones.


~~EMMS~~ ~~EMMS?~~ ~~Emms probably~~ ✓ EMM[...]

Castile, Armetwell St. [C73 v.5. SF 1.0 1021. 130K] Probably L.Fac.

Greyish-cream, fine-textured, with thin streaks more ^{brownish} pinkish-tachy near both surfaces; some quartz, pebbly inclusions with rare black & r/b inclusions; slip a matt brown - very brown. Well-worn; tituration quartz & brown ^{s.s.} surviving. -

~~Castile~~ ~~say~~ EM1 Fabric unknown. Form might fit Castile or equally Scotland. Form acceptable as EM1 Slip a dull brown just normal. ^{?Scoriae!} Reminiscent? Nine valley (or previously not) Dr. 27cm. Part of what may be a rivethole ^{evening} -

1301 - Calle Huichapan St

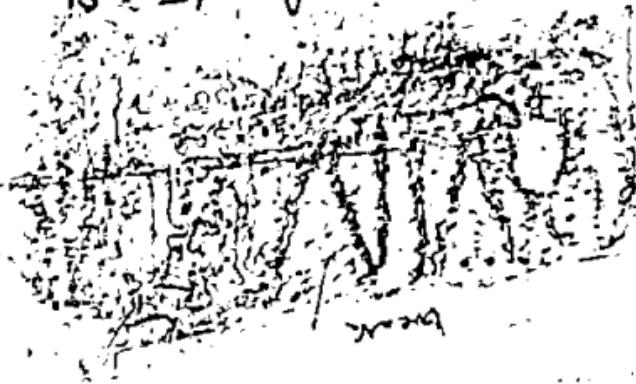

Maryport [CW² \times V p. 164 read as ETI, no information SK] Slightly

sandy, cream fabric with brownish cream slip; light grey, quartz ~~inclusions~~, medium-sized, rounded Tinulation grit. E could well be beginning.

Carlisle [2049 | 2048 | 2082 | 2304 | 2052 | 2067 | 2051 ; 109 K] r. facing

orange-brown fabric with moderate fairly well-sorted, quartz inclusions; cream slip, thinish; Varn. Tinulation Angular quartz probably = all of grit. Probably Carlisle area.

Carlisle [2062 B(757) 82 ; Castle St.; joins 2065 B(677) 2 ;

108K Hard cream, slightly yellowish + greyish fabric; moderate sub-rounded quartz + occ'l red-brown inclusions; cream slip, brownish in places. All surviving tinulation is quartz. Slight burning. L. facing

ELIVS FPL

Uncertain.

H&L [p. 125 no. 3; noted by Dr. Hawerfield; now lost]

CAMBRIDGE.

CAMBRIDGESHIRE.

A. & B. INV. SH. NO. 100. The Provenance Unknown. Museum of A. & E., Cambridge

MASC

See Mascellio

~~PROSECCO~~ o MARCELLO ?

See ENNIO

V. EMIE

Probably as WILDER POOL etc.

Quoted by Bushe-Fox Richborough I p 88. In Northampton Museum.

(not seen at Northampton Mus.)

E O A B

Thruston, Norfolk [unpublished save Arch J.v.14b. p365; 64.949, 72K]

Norwich M] ; buff fabric ; 2 stamps close together ; medium sized white, black, reddish, white grit

Northwold, Norfolk [Th. Bateman, Assoc. Journ. 4, 1849 p.382]
B.A.
CIL VII, 1336, 1331 (as Samian).

Brampton [93K Norwich M. Kiln E. 1967 E/2] r. facing slightly sandy, drab pale grey fabric, misshapen but waffle; stamp a poor impression

Billingsford [Site 7206 - 2K] rubbing and drawing by D. Gurney.



K72 Threeston

E.P. P10.

H62 Drawing No 811

Pit 4

Hartshill [Mrs. M; 586] hard cream fabric with v. thick
brownish pink core; Surface un-fired to greyish buff;
1 tiny brown grit. D=10" Moderate inclusions of tiny quartz
with a few black iron slag fragments. Dr. no. 811 DIE 1

Hartshill H61 ③ 1.5 Incomplete rim section, retrograde, DIE 2.
Slightly micaceous.
Fine-grained cream fabric, moderate inclusions of tiny
quartz and red-brown fragments. Trituration grit 3,
black refined pottery fragments. Internal diam. 25 cm.

ERUCANVS

✓ F.12 5512 small Great Holme St.,

Leicester [715 A 77 1975. 185K] Flange fragment. Different
pot from 179 Kelt. Stamped twice close together. Fine pinkish cream
fabric with ^{dark} cream core. Quartz & red-brown tempering. no

Clay & Mello 1985 Fig 32 no. 9 Bath have site 8.

Leicester [A.312 1960 B v/s. 201K] Flange fragment. Fine
cream fabric with quartz & red-brown inclusions. No trituration
R. Birley grit survives, of b

Vindolanda [v568.12k] IRS. Double stamped. Greyish-cream
fabric with pale orange core, fine texture, little quartz

inclusions and black fragments. No trituration survives.

Desmond Cleary, T.Ferns 1991a p. 64 no. 5 and fig. 29.

Rochester [RO 86 II 1264 56K] vitre. Bitut. 3 joining pieces. c 1/3 of

rim upper part. Dr. 32cm Hard, cream fabric with slightly bluish core;
some quartz inclusions; trituration solely quartz-rounded. In non joining Bodcwt
base sherd. △

Bethune p 47, sub and p 58 no 33

5 RUCANUS

Clay & Pollard 1994 ^{p.26} Phase 2A
(exhibit 1.)

Leicester, Redcross Street [A 316. 1962. 251 + 253. Archive Illustr 3.

MK + MN. 238K.] All of rim survives; stamped twice close together on right facing side of rim only. Surface of vessel flaking and weathered & discoloured to greenish hue; lower inside surface very heavily worn indeed. Dr. 30 cms. Fine, cream fabric with few quartz inclusions and occasionally red-brown fragments. Trituration grit almost entirely opaque white, translucent & occasional grey quartz; occasional red-brown sandstone & rare cindery black (iron rich?). Clay and Pollard 1994, p.92, 152-153 - published as 2 mottana but thought to be only 1 by me.

ERVCANVS

(with)
22/2

C

F39

Archaeo. illust 7. p.66, no 4 Phase 2a
p.26

Leicester, Redcross Street [A 316. 1962. 239. MP. VII 38. 234K]

R. facing single stamp on FF and joining CRS with spout,
slightly burnt. Cream fabric, moderate inclusions of fairly
ill-sorted quartz (upto 1mm.), sparse red-brown fragments.

Trituration grit ^{001327-233K} quartz. Dr. c: 33 cm. uncertain P.T.O. →
Slightly burnt before fracture. Clay & Pottery 1994, 92, ^{no.} 151
Phase 2A (p.26) early 2nd century.

Spout does differ slightly from other three.

4th vessel, attributed to ERVCANVS, CRS with entire spout

but no stamp. [A_316. 1962. 242. KT IV 30 Redcross St. dug
by Max Hebditch] Heavy, thick vessel. Brownish-buff fabric
moderate inclusions fairly ill-sorted, sub-angular
quartz (up to 1.5mm.) ; orange-brown fragments fairly common.
^{some}

Trituration grit mainly quartz with some black fragments.

Dr. 32 cms. Surface ~~is~~ orange-brown looking like a slip,
big grey patch on outside. Large iron slag fragment stuck in
outside v. Heavily worn. Not enough survives to have
the stamp but it's so like 233K that it must be Eracus.

ERUCANUS Clay & Pollard 1994, Phase 2A(^{early²}~~mid¹~~) p 26

Wincanton, Redcross Street. [B316 · 1962 · 252 + 250 MN + 198]

Archive Illust 4. VII N(MN/MK join) F39②. 233K] r.facing
stamped twice close together, left side does not survive.
Fairly hard, fine, pale brownish cream fabric with few quartz
inclusions, some red-brown inclusions; tinteration mainly quartz
with some red-brown fragments. Dv. 34cm. Worn but not heavily

ERUCANUS

Rochester [Northfield.
RONO1 8015 93K) r.facing. Archive 116.

Incomplete rim-section. 80 gms Diam c 340 mm 7%
Ruth's Fabric 10 with some possible traces of concentric
scoring. Hard, fine-textured and smooth, cream fabric.
cream slip or glaze to exterior (slightly darker)
Inclusions: ill-sorted and random, quartz (transparent) with
flecks of red-brown material. Orientation: all quartz a
small sherd except for 1 blackish rock. Probably Hanclter/H

(5)

ERUCANEUS

Northfield

Rosette [RON 01 8004 94K] r. facing stamped

twice close together. 430gms Diam 310mm 13% Fabric 10
(R. Iron). No sign of wear or cracking sherd.

Hard, smooth, very well-fired cream fabric.

Inclusions: fairly frequent, mostly tiny red-brown material with few larger quartz. Tauturation:

abundant to \leq .5cm below bottom of bead; small to largeish, all quartz, but 1 glz sandstone spotted.

It looks as though gritted has been added over some kind of concentric scoring. Accepted as M-H(s)

ERUCANUS ~~the~~ Shire's; Little Lane Phase 5.1 TPQ earliest to
2665 1st half 6th

Leicester [A 39 1988/1537 E=38.3 257K] since slightly diagonally
but break too close to sample to show if stamped more. Likely to
be L-fac but not certain. Dr. 34 cm. (Cream fabric with brownish
slip. Inclusions: ^{moderate +} ill-sorted, mostly quartz with some f-brown & v. rare
^{dark; small} feldspar. Interruption: mostly quartz, some r-b. sandstone containing
quartz, rare: haematite. Medium + coarse to c 1 cm. below b. Abnd,
stragglers above. Well-worn. Slightly burnt. 3 young sherds. 3
(Phase 5.1 TPQ early?)

ERUCANVS

Northwich [43K + 52K Castle Dairy z 31/3. Cat. No.

L① F① E 52K+stamp. z 31/16 1974

2330 - 1977 + / flange fragment not joining but same vessel. 29/3/74. Surface grey, buff underhalf.

43K is Hard buff cream fabric, pale grey in core; heavily tempered. Also 2 basal sherds possibly same pot.

Grit mostly quartz, some black. (See 1980). Weaver Hall

43K is 3 joining flange fragments.

Wall [WL] v (+); J. Gould] fine, cream fabric with tiny fragments of red-brown grit in it. Flange fragment; stamped twice close together. Maudessemum ["The Furlong". 1964. Casual Find 52K] flange fragment. stamped twice.

Tripontium [Sent Feb. 1969. 20K Sc. 915 | Section C SF 389] Flange fragment. Fine cream fabric with pink core; contains very finely broken grit & b & ? quartz. + ^{Creamy white st?} Leicester [22] 78 (1975 179K] flange fragment; cream fabric with dark charred cream slip, greyish in parts. Quartz & red-brown tempering. L-facing sketch. Inclusions almost fairly frequent. (S) Butt. vessel

ERUCANUS

Staffs

Barton-under-Needwood [6936:01] 965 ② 2K] r.facing.

stamped twice close together. D. 30 (14%) Hard, pale brownish fabric (sandy coloured) brownish-buff fabric. Inclusions: more than moderate as Tinteration. Rare large sandstone fragment in fabric. Dasher slip? - fused to grey on flange. Tinteration grit: some has fallen out. Was probably close packed up to ^{date to} bottom of head. Mostly quartz, some opaque black, could be slag; haematite nodules. Ill-sorted, angular

ERVCANUS

This piece was lost at Weaver Hall in 1980

Northwich (C.N.R. P.4.. 2K) ret. facing. Stamped twice close together.
Fine textured cream fabric with fine sandy particles; medium-sized
white, red-brown & grey grits. See other notes. A

Doncaster [F/GATE 1985 IA-C] IN/25. 72K] Hard cream fabric with brownish
buff slip - traces of. Flange fragment. Stamped twice close together. A

*Warrington [IB:1:1 43K] Flange - likely to be Ervecanus but
cannot be atttrib. with certainty. Heavy, hard cream fabric;
pink in parts. Midland origin; deep flange. COUNT
University College London [Rubbing 75k. sent by R. Reece]

Stamped twice close together. See rubbings. Dept. of Archaeology?

ERICANS

Kirkby Thore [D.C.W.S. 1962. KI II / 61/C 7] See letter 7. 3.62] fine,
cream fabric with certain amount of tiny v.-b. grits in it; Intivation
grit; abundant pebbly translucent whitish quartz-like grit to bead;
medium to smallish to small - very heavily gritted; stamped
twice together; D = c. 14" (Letter 7 III 62. not securely
placed but thought to be from the pre-stone fort).

Ribchester [RIB 78 BH 139 1. 51K] Bathhouse. unstratified.
Light beige & ^{dark} cream fabric with some pink in core; with fair
amount of quartz & occasional vlp & blk inclusions. Stamped
twice close together. D. c. 4-4 cms.

ERVCANVS.

Wielderspool [417'13; broken; probably different vessel from 3K; 54K] Mayo

[label, but no provenance on card] cream fabric with slightly pinkish tinge;
small to largish greyish brown grits to bead; B.F. 34. Worn.

Leicester [L.P. 37.3; C 31/2 P, Fenny Wall; not the published one] S. ch.
fragmentary stamp, asby; white pipeclay; no grit. at Institute of Arch.

Bainbridge [B.R.H. 1961; B:61 C(5)] hard, creamy white fabric with
a few grits in the body of it - one red-brown & 1 dark grey. Others &
the closely massed largish to smallish white (quartz?) & grey grits
right to b.b., stamped twice together. In Flavian-Trajanic
deposit outside the ^{east} ~~west~~ gate. ⁹⁰⁻¹²⁵

Wilderspool [May p. 64; Warv. MTA 13' 13] stamped twice close together; creamy white fabric, pinkish in core, may have had slip; flange only.
from Hope-Masham Collection bought at Sotheby's 1948.

Templeborough [Tildyard Collection] hard white pipe-clay with tiny grits;



Wroxeter [1912 p. 66 fig. 16 no 11] Type 38.

Leicester [p 217 + f. 58 no 7] ^{seen, rubbing} Jenny Wall rather coarse dirty light buff, with sparse grey brown grit; traces of buff slip on rim and exterior wall. Quite a separate vessel.

Ribchester ^(?) hard, white fabric; much grey & light brown grit up to the head; very battered; reading difficult. CHECK



Templeborough.
(Donovan by Hildyard)

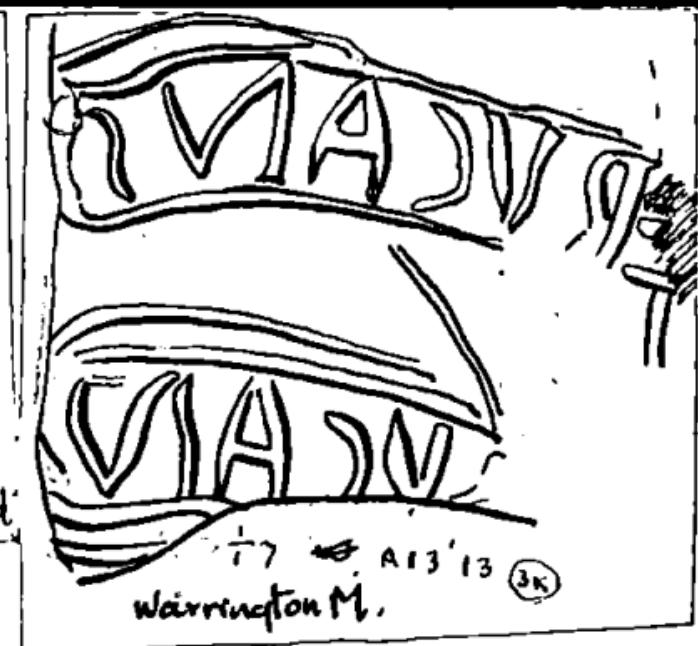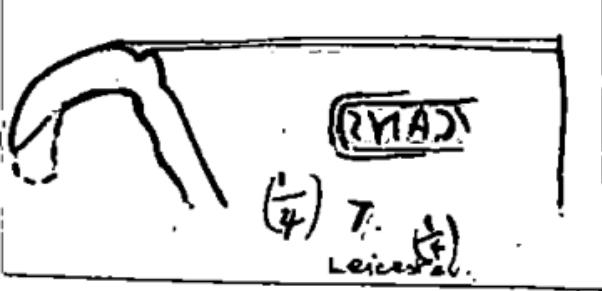

^M heicester [3K; 859] ^{gold number.} stamped three close together; yellowish buff, orange-buff
core; patchy brown and buff surface. As. Ware. vi.

heicester [23K, St. Martins. 3' 2" f. 18.8" mhd] hard, slightly sandy, white
fabric; medium brown and grey grit. Die as Ware. Mus.

heicester [30K ¹⁸⁶⁴ no. no. M.2, St. Mary's & W. bridge] yellowish buff fabric with orange-brown
surface; brown and grey grit. [30K or 39K Driddage ^{DC} ^{Re-enforced} _{As above.}]

heicester [39K no. no. M.52; broken?] white fabric; brown and black grit.

Alaudra Castle [Derby At N.S. J. xxix, p. 25, figs no. 64, 9K] smooth, cream with brownish
buff slip; whitish & some blackish grit, prolific on fragment to b.b. flange broken.

Ribchester [In Rectory Garden 1958] ^{south Pidgeling.} 19K smooth, creamy buff fabric with v. sl. pinkish tinge.
Inside, after red-brown frags. probably like infabric; few grey grits on flange; few v. tiny wh. & grey grits at top,
stomach - least twice.

ERUVIS

Birleyan reading of 'Caerleon' stamp.

Barr Hill (Hunt. Mus.); 21 V VE

'Rim Antonine, E.B. thinks Caerleon legionary wave.'

ESAMI HERINGHAM KIDS? INCORRECT?


Caistor by Norwich [unpublished D.48; 13K] orange buff fabric with somewhat paler buff core; a few, medium + large, black + white grits on fragment

Caistor by Norwich [Naf & N. AS. xxvi pt ii p. 213 R 27; D 34, 67K] pinky buff fabric to grey-cream surface, grey in parts (burning?); sparse, medium black grit. Pit 26.

JRS X V p. 136 stamp not mentioned

Heringham [Kiln II, 21. 954; E.O. Benton, Norwich M. 35K] soft, muddy, light brown fabric with one black grit surviving; stamp almost erased but reading certain; some tiny ?waster cracks in surface.

Journal of Roman Studies (1960 p. 228). Note incorrect.

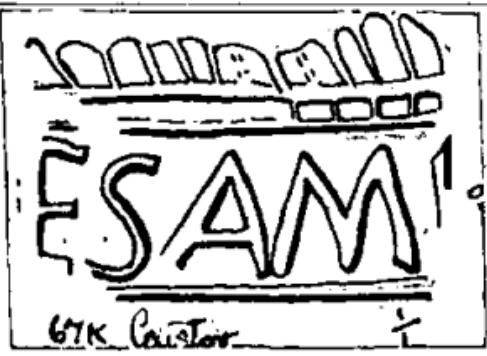

67K Castor

Stoke Ash, Suffolk [SAS019 - ^{Tyr} Trench 1 ORL 4 Site run by
Mike Hardy, 29 High Rd., Westwell, Harleston, ^{Suf} Norfolk
IP20 OHG Info from Gilbert Burroughes] 300gms
Pr. 290mm. 13% assumed facing. Hard, pale,
pinkish-brown with medium grey core merging
into the surface colour. self-coloured. Inclusions:
fairly frequent, ill-sorted, but mostly tiny + small,
quartz, black + some red-brown material + flint
with a few larger quartz and flint. Tiny
inclusions visible on surface making it feel slightly

HONDON, Basinghall St. (BAZ05)

LVCIVS	2	<496>	2149	Pd 5	✓ 806K
VALENTINVS	2	<2733>	1667	Pd 4	✓ 807K
MAXIMVS		<2734>	2734	Pd 4	✓ 808K
HERRINGBONE Y.		<2735>	1665	Pd 4	✓ 809K
SEVALVS					✓ 810K

abrasive. Inter alia: quartz, flint, soft cream
pellets (non-reactive), red-brown & quartz
sandstone. Condition: worn. Fragment
from top border!

EXOMIVS see MAY . . . See EXOM Uncertain
See p 478 Catterick for Phoenix forms

Cotbridge [unpublished; no. no. 79K] dark grey core to orange, with cream

slip; largest medium, r/b, grey, black grits to near b. b; flange broken.

Catterick Village [north side; found Craft Andrew; 19K] L-facing; rather gritty
fabric with small grits in it; hard brickish orange with grey core and
cream slip; largest to small, brown, grey, blackish grits. P. 16
^{93° C. 1. 81. b.}
^{p 342, MS 66}

Ambleside [Armit Library; unpublished GK] EXOMF; reddish fabric with cream or
buff slips & grey core - flge + upper part; largest media, red-brown + white grit; L-facing

Catterick [1959 K XXIII (18); 19K] flange fragment; orange brown fabric
with grey core, & cream slip. Check? EXOMV S

Many pots - assigned.

looks like EXOMUS but fits no known die.

486

Cattonick [1959 K XXIII 18] 26K] FF. orange-brown fabric with grey core
+ cream slip. (p 340, M549 Phase 3 - 4)

Carlisle [Civic centre site 96K 49.1965-6] Hard, orange-brown
fibre, with thick black core & creamy buff slip; mostly white but some
v/b grit (intercation).

Carlisle [83 MKT A \oplus 163K] r. facing. Dr. 26cm. Very hard,
(overfired) almost chocolate colour with quite bright orange-brown
core. Inclusions: moderate / fairly frequent transp. and white quartz,
rare darker grits some probably black, some perhaps ^{sooty} dark
red-brown. Intercation: mostly as white and transl. quartz; could
have rare other ones but no obvious. Barely if ever used - very
sharp & fresh. If there is a slip it is self-coloured. Hard

enough to be a waster but no sign of being mishapen. No obvious
sign of use. It looks as though the grit is slightly embedded & the clay
split open above it - the friction on it could just be slip.



EXSO

Birdoswald [cw² ~~xxx~~ p. 189 no. 7; Tullie Ho. 34K] ? r. facing; hard,
red-brown fabric with buff slip mostly gone; fair amount of black, r/b,
brown and white grit, worn to b. b.; vessel made up; D = 8⁶/₁₀ ins.

Cardurnock [cw² xlvii p. 119 no. 4 on fig. 14; S. R. (4); Tullie House 47R]
Stamp faint; EXSI read by B²; soft, light orange-brown fabric with
cream or buff slip; no grit on fragment; fabric deteriorating on flange;
From within the south rampart toward the south-west angle.

Birrens [1965 (359) & 273] joining Hunterian M.] orange brown
fabric with grey core & traces of cream or white slip. Hole
drilled through flange.

INCOMPLETE

Possibly also Cathericke MOY

EXON

Ebchester (PSAN² IV pl86),

ATTRIBUTED

Baines [Border only 16.1998 (224) 9K] Rim form would fit Saxon but stamp could only fit his die 4 (1 example only). The border is more likely to be EXOMVS see 2K Catterick Racecourse. Hard, orange-brown fabric w/ white streak. Some ill-sorted quartz. Intersections mostly quartz; flint; rare red-brown. Cream slip.

('A fragment of a R. molar has been lately discovered at Ebchester with EXON')

Fabric 1963 - brown fabric ; translucent white + grey or black.

XOM

Bowes [70, IV ④3] v. facing. Orange-brown fabric basically fine textured & soft
with grey core; fabric contains white & red-brown inclusions; cream slip; white,
grey & brown glits to near bead - small to largish. 2^h Arthur no. 123
Catterick [Catterick Bridge, Trial Excavations at E.S.W.
Hildyard & W.V. Wade in YAJ Part 147, 3rd part of vol.
XXXVII (1950) p 41b, no. 45 417] E.B. Birley "The fabric is
reddish buff, cream washed, blue in fracture. Stamp reads
J X O M presumably Mox ret. with indications of a line
below — Potters name no doubt Moxius, this date,
to judge from fabric: c. 150." Not seen. See folder for
card with duplicate entry & p. numbers etc. Different pot from 1961 Craft Andrew

E O M

EXOMVS

EXC M

Different die
marks

Maryport [4K A.M.2. Netherhall Collection] orange-brown fabric,

pinkerish thick core; cream slip.

54-40

Catterick Racecourse [273-65-~~35~~³⁵, 57-140] all joining &

(P) 1+2 + p 479

273 23 (22/23) ^{not joining} _{inclusions, mostly} 2K. Hard orange-brown fabric, ^{thin} grey core; moderate, ill-sorted quartz with some largerish though sparse red-brown inclusions; no texture mostly quartz, occasional red-brown & rare opaque white material Dr. 27 1 stamp on 273 65 (3) the other on 273 (23) (23); Remains of thinish white slip. (Fabric).

Catterick Racecourse [273-10 (15) 3v] L-facing. IRS. similar fabric but finer textured and may lack the brown inclusions; no texture survives traces of slip. Too small for Dr. v/s p 478

See Catt 478-9 for note on Exodus

2K Hadmamic to early Ant.